

Failure evaluations in bucket conveyor. Studies case

Evaluación de fallas en un transportador de cangilones. Caso de estudio

HERNANDEZ, Herrera Hernan [1](#); CASTELLANOS Luis M. [2](#); CABELLO Eras Juan J. [3](#); SILVA Ortega Jorge I. [4](#); MANGA Carlos A. [5](#)

Recibido: 14/02/2017 • Aprobado: 02/03/2017

Content

- [1. Introduction](#)
- [2. Material and Methods](#)
- [3. Results and Discussion](#)
- [4. Conclusions](#)
- [References](#)

ABSTRACT:

A failure in the bottom sheet of a bucket conveyor (KZB-Q.AUMUND) during service was investigated. Sheets are coupled to the chain through a screw connection; they operate in variable load scenarios causing fatigue. A chemical and microstructural analysis was made showing that sheet was built in steel with 0.15 % of Carbon without alloying elements that contribute to the refined grain and resistance increase. Strength calculation, used to determine safety factor, consider load system and type material. Results concluded that geometry and thickness value do not provide an adequate fatigue resistance coefficient.

Keywords: bucket conveyor; failure analysis, fatigue resistance, finite element analysis.

RESUMEN:

Es investigada la falla en las láminas del fondo de un transportador de cangilones KZB-Q.AUMUND durante su servicio. Las láminas están acopladas a una cadena a través de uniones atornilladas y operan bajo un régimen de cargas variables causándoles fatiga. Se realiza un análisis químico y microestructural el cual evidencia que las láminas fueron elaboradas de un acero con 0,15 % de carbono sin elementos de aleación que contribuyan al afinamiento del grano y al incremento de la resistencia. Se calculan las tensiones para determinar el coeficiente de seguridad a la fatiga considerando el sistema de cargas y el material de las láminas. Los resultados concluyen que la geometría y los valores de espesor no le proporcionan a las láminas un adecuado coeficiente de resistencia a la fatiga.

Palabras claves: transportador de cangilones; análisis de falla, resistencia a la fatiga, análisis por elementos finitos.

1. Introduction

In cement industry, a high number of raw material and products are processed and transported during manufacturing process; those involved equipment have significance in company's productivity.

Conveyors used to drive raw materials in cement industry usually are bands and bucket conveyors. The last ones are used commonly in Clinker transportation and finished final products which are driven to storage rooms. These systems are selected according with material properties, load requirements and lifting [1], [2].

Mechanical failures are usually attributed to non-compliance maintenance intervals, errors during design such as material selection, assemblies or incorrect operation [3], [4]. These failures conditions are in disagree with industry expectances which specify that critical equipment must be defect-free and systematic failure that cause stops in processes, increasing operation cost and delays during deliveries, affecting finances due to markets requirements and competitiveness [5]-[7].

This paper analyze a case study to determinate failure causes in the bottom sheet of the bucket conveyor KZB-Q Clinker Conveyor-AUMUND in Colombian Cement Company. The reviewed unit evidenced four failures between July and December 2015, producing considerable financial losses.

In order to identify failure causes a chemical and microstructural analysis at material using for bottom sheet manufacturing was carried out, also mechanical properties of the material were studied and resistance to fatigue assessment was developed [8-12].

2. Material and Methods.

2.1 Material Characterization

Fig. 1 shows location and magnitude failure in the analyzed bucket conveyor. The chemical analysis to the specimens of the bottom sheet was performed using an optical emission spectrometer OLYMPUS GX41. Nital solution of 2% was used as attack element.

ASTM E-3 [13], E-407 [14] and E-45 [15] were used for preparation, chemical attack and non-metallic inclusions calculus respectively. A tensile test was realized in specimens using ASTM A-370 [16] using a 60 tons Shimadzu universal Machine. The media Brinell hardness was obtained in a Wilson Hardness Tester using ASTM 92-82 [17].

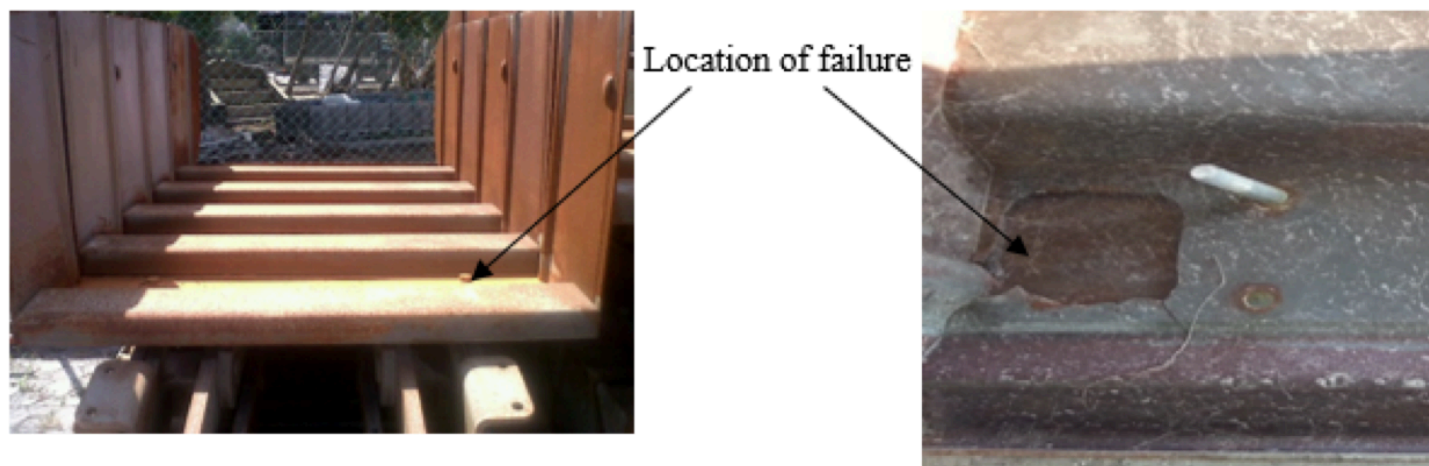


Fig. 1 . Failure location and magnitude.

The fatigue resistance coefficient calculus begin using a free body diagram representation in order to obtain loads that appear on the bottom sheets conveyor. Sheets were drawn using Mechanical Desktop 6.0 and with calculated loads, it is modeled using finite elements method with the software Cosmos Design Star 4.0. With the stress values and load cycle effort it is calculated the sheet fatigue resistance coefficient.

3. Results and Discussion

3.1 Material Characterization

Chemical analysis

Results, showed in table 1, evidenced that steel used is carbon steel without alloy elements and micro-alloy refined grain. The low carbon level guarantee an adequate weldability but this reduce hardness property, mechanical resistance and fatigue resistance.

Table 1. Chemical analysis on the bucket sheet conveyor

Element	wt. %	Element	wt. %

Carbon	0,149	Molybdenum	0,014M
Silicon	0,213	Nickel	0,086
Manganese	0,599	Copper	0,292
Phosphorus	0,14	Aluminum	0,0067
Sulfur	0,041	Titanium	0,0015
Chrome	0,086	Niobium	0,018

Micro-structural analysis

Specimens without attack showed nonmetallic shapes derived from Type A oxides. Using chemical attack, it was detected high ferrite levels and very low pearlite presence as is shown in a micrographic analysis presented in Fig. 2 .

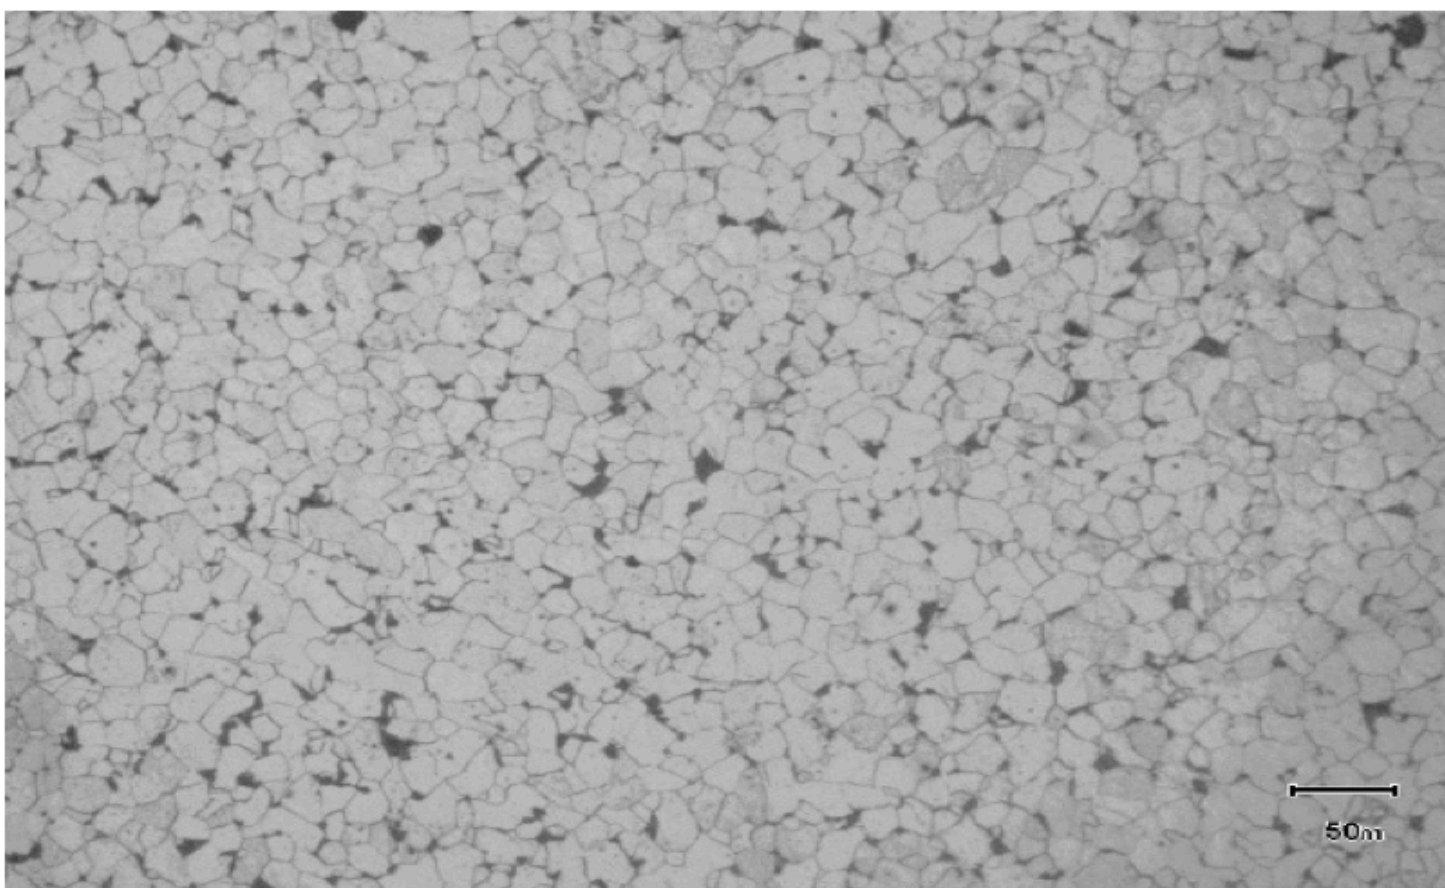


Fig. 2 . Optical micrograph analysis

Mechanical Properties

The steel average hardness was 135 HB, otherwise the average mechanical resistance measured were 223 MPa in the yield strength and 345 MPa with the maximum tensile value, they correspond to the structure type and low carbon steel percentage.

3.2 Forces influencing on the sheet

The conveyor operates with a transmission chain joined to the bottom sheet using screw connections. Two wheels located at both ends support this; connections between wheels and conveyor is realized through wheels axis, which is fixed to a "U" profile, welded in the bottom sheet. The distance between the farthest Union "U" point and the wheel support is 177 mm as is shown in Fig. 3 .

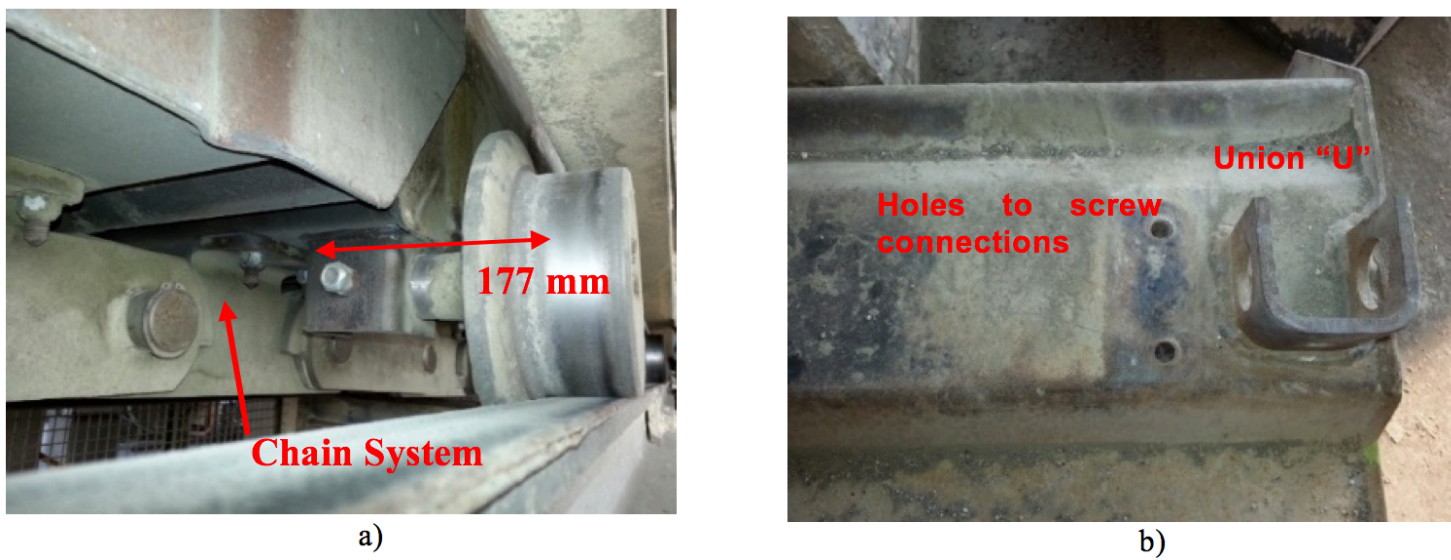


Fig. 3 . Joint elements of the bottom sheet with chain drive and supports.

Forces values on the conveyor were calculated using information provided by industry. Conveyor moving parts weight has a value of 4.84 kN/m including chain transmission. The maximum Clinker weight value deposited in the conveyor is 3.1 kN/m. As is shown in Fig. 4 , the distance value is 1.5 m; the maximum weight value is presented in Fig. 5 and determined as follow:

$$TW = (WMP + MW) \cdot 1.5 = 11.91 \text{ kN}$$

Where:

TW: Total weight

WMP: Weight of moving parts.

MW: Material weight.

1

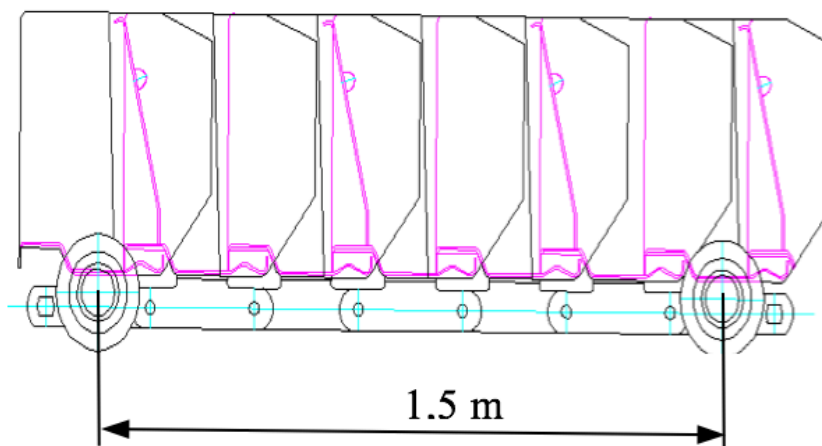


Fig. 4. Roller distance

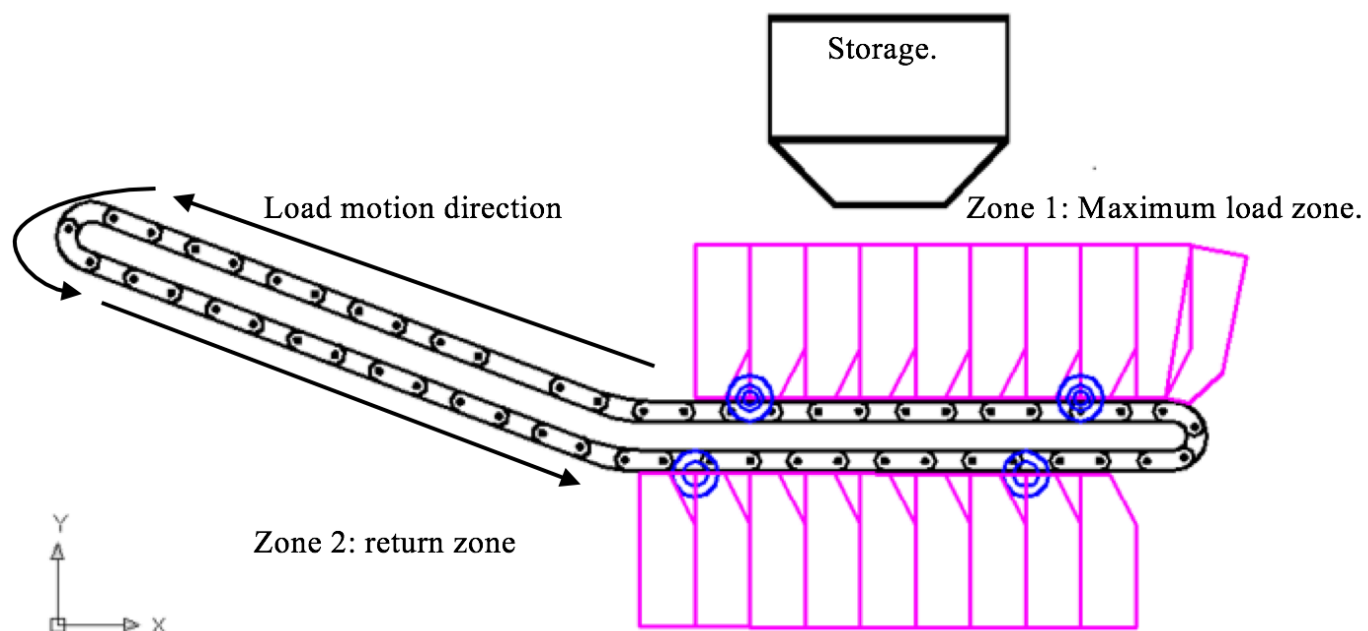


Fig. 5 . Bucket conveyor KZB-Q Pan conveyor – Aumund geometry.

Considering the total weight (TW) and taking into account that the system is symmetric, on each wheel is registered a force reaction of 5.59 kN. Reactions in the return (zone 2) only consider the weight from moving parts obtaining a reaction of 2,42 kN.

3.3 Tensile Values

In order to realize fatigue analysis, there were calculated tensile values in both zones:

- Zone 1: Moving parts weight were considered while the conveyor was loaded.
- Zone 2: Considering only moving parts.

The maximum force value in the sheet is applied in the farthest point from the “U” weld point. The force is transmitted from structures supports using the axis lane as is shown in Fig. 3 a). The sheet was modeled using the software Mechanical Desktop 6.0 for the design and the software Cosmos Design Star 4.0 for simulations. During modeling, there was considered a parabolic tetrahedral mesh, it allowed better results in order to have an adequate contour representation [18- 21]. In all models was realized a progressively convergence refining study until obtain a difference between stress value for the definitive model and the previous model with a value lower than 5%, ensuring that local maximum stress values do not depend from the used mesh size [22], [23]. Using finite element method it was obtained for the forces in zone 1 a stress value equal to 89,7 MPa and 32,42 MPa for Zone 2. These results are shown in Fig. 6(a-b).

As it is observed in Fig. 6 , the sections where was located the maximum stress value correspond to the failure section as is shown in Fig. 7 .

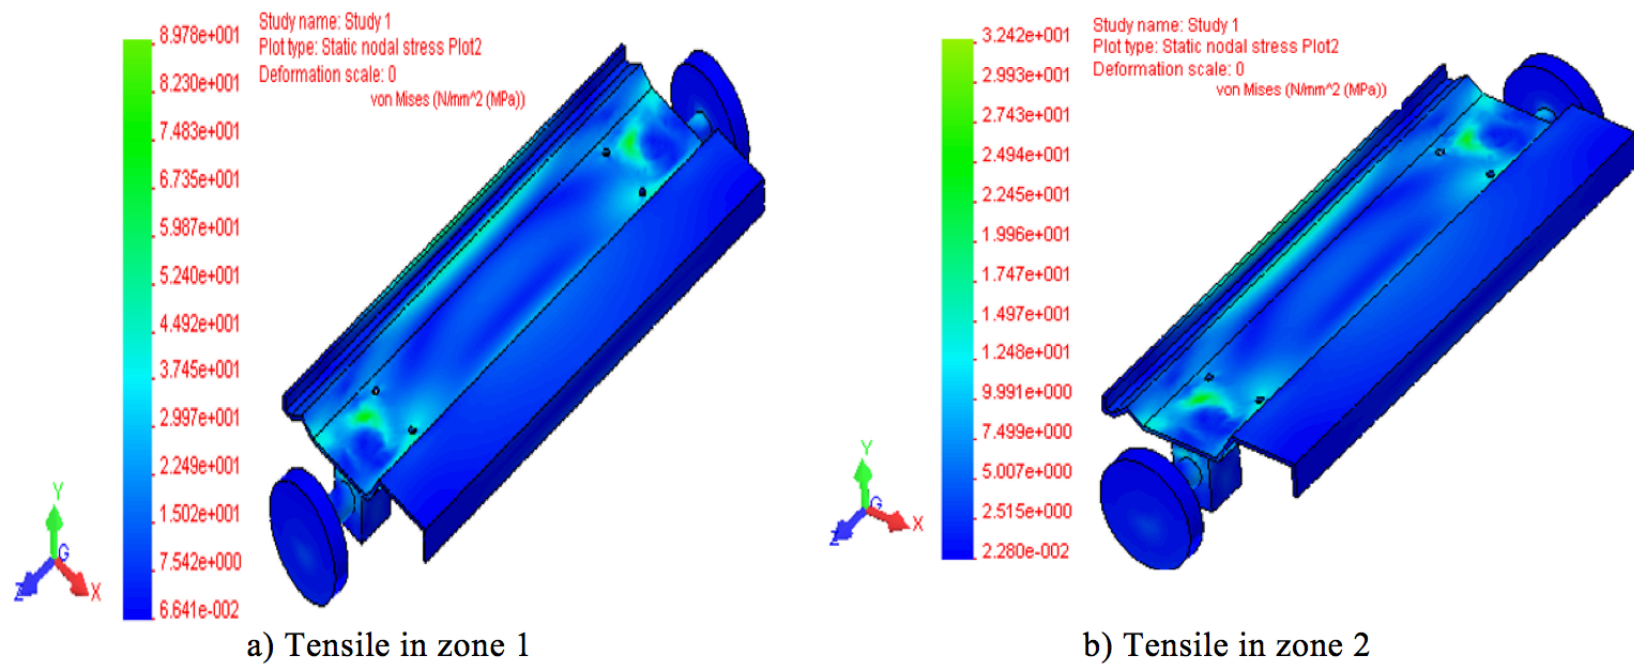


Fig. 6 . Support the axle of the wheel in the bottom sheet conveyor and Tensile in zone 1 and 2

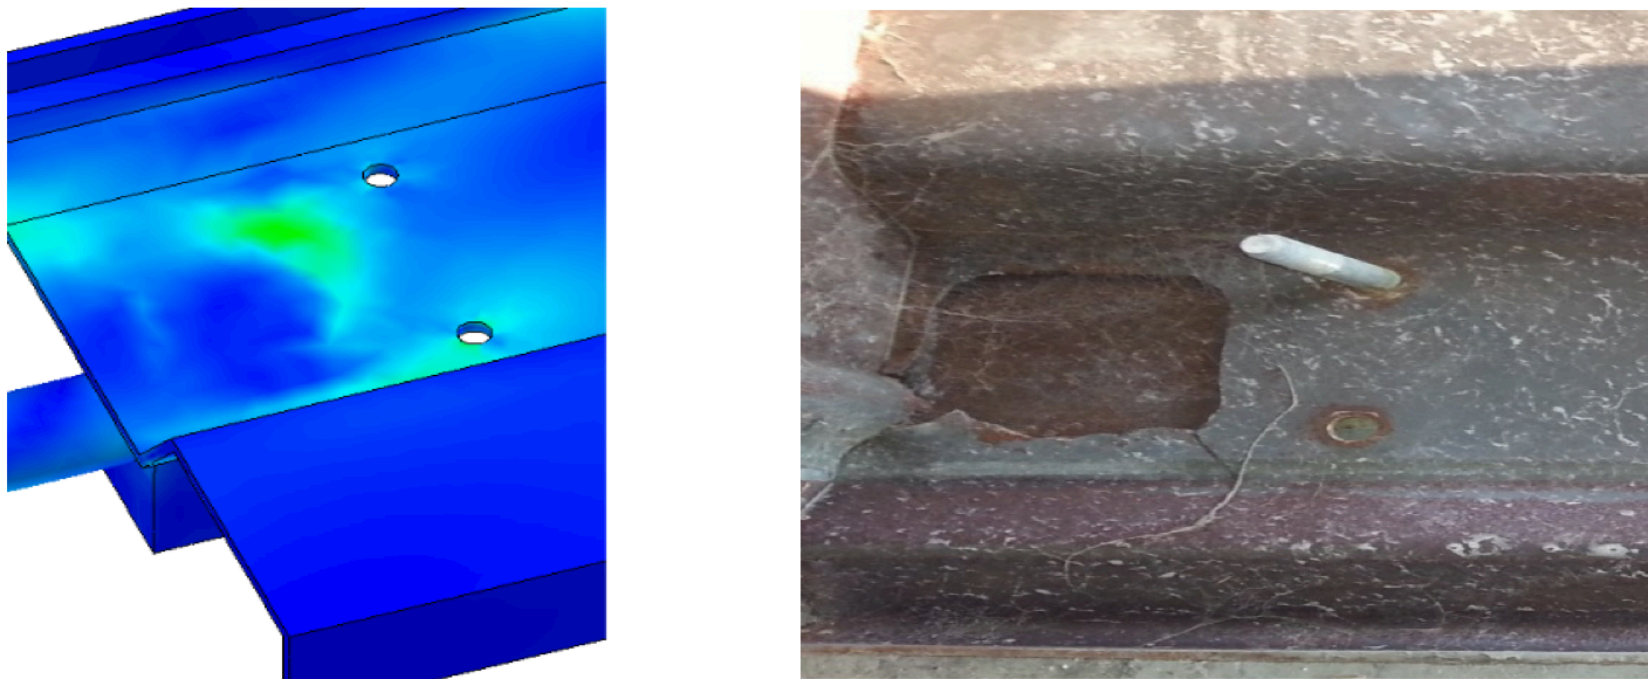


Fig. 7 . Point where the stress value of the sheet is maximum and place of the failure.

3.4. Asymmetry coefficient, medium tensile and amplitude tensile.

Fig. 5 evidenced that the conveyor bottom sheet has worked using variable stress values during

operation. For this cycle there were determined the asymmetry, the average tensile during the cycle and the amplitude tensile value [8].

$$r = \frac{\sigma_{min}}{\sigma_{max}} = \frac{-32,42 \text{ MPa}}{89,7 \text{ MPa}} = -0,36 \quad 2$$

$$\sigma_{med} = \frac{\sigma_{max} + \sigma_{min}}{2} = 28,64 \text{ MPa} \quad 3$$

$$\sigma_{ampl} = \frac{\sigma_{max} - \sigma_{min}}{2} = 61,06 \text{ MPa} \quad 4$$

Where,

r: asymmetry ratio.

σ_{med} : medium tensile cycle

σ_{amp} : Amplitude Tensile cycle

3.5. Fatigue Safety Factor.

The fatigue safety factor for a cycle must be $-1 \leq r \leq 0$ according with [8], as follow:

$$n_r = \frac{\sigma_{-1}}{\frac{k_{-1}}{e_s * e_e} * \sigma_{amp} - \frac{\sigma_{-1}}{\sigma_{rt}} * \sigma_{med}} \quad 5$$

Where: $\sigma_{-1} \approx 0,5 \sigma_{m\acute{a}x} = 170 \text{ MPa}$

For the reviewed case:

$$n_r = \frac{\sigma_{-1}}{\frac{k_{-1}}{e_s * e_e} * \sigma_{amp} - \frac{\sigma_{-1}}{\sigma_{rt}} * \sigma_{med}} = 0,85$$

The coefficients of the equation were taken from [24], [25] and their values are presented in Table 2 :

Table 2 . Coefficients used for Fatigue Safety Factor.

Abbreviation	Description	Value
K_{-1}	Tensile concentration factor	1,70
e_s	surface quality coefficient	0,68
e_e	Scale factor coefficient	0,72

The Fatigue Safety Factor is very low, for that reason the bottom sheet conveyor will fail after a number of operation cycles as has occurred previously during the process. A bottom sheet with better properties such as ASTM A 715 80° could be a feasible solution [26]. This steel has low carbon content (0.15), it provides good weldability and better mechanical properties because its yield strength is 520 MPa (higher than the used) and its maximum tensile value is 620 MPa (higher that the used). These

values increase the Fatigue Safety Factor as follow:

$$n_r = \frac{\sigma_{-1}}{\frac{k_{-1}}{e_s * e_e} * \sigma_a - \frac{\sigma_{-1}}{\sigma_{rt}} * \sigma_m} \quad 6$$

$$n_r = 1,56 \quad 7$$

4. Conclusions

Bucket conveyor was made with a standard steel with low carbon content, which implies a low mechanical resistance and good weldability. The resistance analysis showed that bottom sheet geometry and thickness does not provide an adequate fatigue safety factor, for that reason after a number of cycles it will fail for this reason.

In order to increase the fatigue safety factor there are solutions such as increase the bottom sheet thickness or replace the sheet with a more resistance material such as the ASTM A 715 80 degrees, it provides an adequate fatigue safety factor.

References

1. L. C. Giraldo, O. Flores, F. Higuera, "Design and construction of a mixer of screw conveyor for dry mortar," *Scientia et Technica*, vol. 2, no. 45, pp. 37-42, Ago, 2010.
2. C. Hernández, "Creación de base de datos para equipos en planta y actualización de stock de repuestos para elevadores de cangilones en una planta de cemento", Tesis de Grado, Facultad de Ingeniería, Universidad de San Carlos de Guatemala, 2010.
3. J. Ledesma, J. C. Rosete, J. Pérez, "Aplicación del sistema RCM en la determinación de la causa crítica de fallo en un elevador de cangilones." *Memorias del XVII Congreso Internacional Anual de la Somim*. San Luis Potosí, México. 21 al 23 de Sep, 2011, pp. 133-142.
4. C.W. Olarte, A. M. Botero, A. Benhur, "Importance of the industrial maintenance inside the processes of production," *Scientia et Technica*, vol. 1, no. 44, pp. 354-356, Abr, 2010.
5. Rajiv Kumar Sharma, Pooja Sharma. "Integrated framework to optimize RAM and cost decisions in a process plant", *Journal of Loss Prevention in the Process Industries*, 25, 883-904, 2012.
6. A. Garofoli, J. Garofoli, "Elevadores de cangilones de descarga centrífuga, pérdidas por problemas de diseño". *Revista Iberoamericana de Ingeniería Mecánica*. vol. 18 no. 2, pp. 55-67, 2014.
7. K. Olivares, M. Arellano, M. López, K. Soler, "Sistemas de información para la gestión de mantenimiento en la gran industria del estado Zulia". *Revista Venezolana de Gerencia*, vol.15, no. 49, pp. 125-140, 2010.
8. G. S. Fernández Levy, "Resistencia de Materiales", La Habana, Editorial Pueblo y Educación 1983, 511 p.
9. O. Araque, N. Arzola. "Estado del arte sobre la integridad estructural de uniones soldadas y modelos de propagación de grietas para la gestión de vida en estructuras". *Revista Chilena de Ingeniería*.21. No 2: 279-292. 2013.
10. Vansil, G. AlShali, A. Failure Analysis of conveyor pulley shaft. *Case studies engineering failure analysis* No 1: 144-155. 2013.
11. S. González, D. Fernández, J. Álvarez, R. Ramos. "Estudio a fatiga de uniones soldadas a tope. Comparativa y validación de las principales metodologías". *Dyna*. vol. 88. No. 2, pp. 171-180. 2013.
12. O. Araque, J Cabello, "Estudio sobre la resistencia y rigidez de ejes huecos" *Revista Scientia Et Technica*. Vol. 1 No 30, pp. 219-224, 2006.
13. ASTM E3-11, Standard Guide for Preparation of Metallographic Specimens, ASTM International, West Conshohocken, PA, 2011, www.astm.org
14. ASTM E407-07(2015), Standard Practice for Microetching Metals and Alloys, ASTM International, West Conshohocken, PA, 2015, www.astm.org
15. ASTM E45-13, Standard Test Methods for Determining the Inclusion Content of Steel, ASTM International, West Conshohocken, PA, 2013, www.astm.org
16. ASTM A370-14, Standard Test Methods and Definitions for Mechanical Testing of Steel Products, ASTM International, West Conshohocken, PA, 2014, www.astm.org.
17. ASTM E92-82(2003)e2, Standard Test Method for Vickers Hardness of Metallic Materials (Withdrawn 2010), ASTM International, West Conshohocken, PA, 2003, www.astm.org
18. Chandrupatla, T., Belengundu, A. *Introduction to Finite Elements in Engineering*. Prentice Hall. USA. 1997.

19. E. Martínez, M. Estrems. "Desarrollo de un modelo matemático de diferencias finitas para el análisis del campo de temperaturas en la soldadura por arco de chapas finas de acero inoxidable". Revista de Metalurgia, 46 No 6: 511-519. 2010.
20. H. Hernández Herrera, R. Goytisoló, J. Moya, I. Jackson, "Nuevas expresiones para el cálculo a torsión de costuras soldadas de filete de configuración compleja. Vol. 3, pp. 27-34, 2006.
21. Felippa, Carlos A. Introduction to Finite Elements Methods. University of Colorado, 2001. 586 p.
22. Cernuschi, D. J., Elementos Finitos. Ejemplo de aplicación. Consideraciones sobre el uso de los Elementos Finitos. Agosto 2003.
23. Chau, T., Besnier, F. Numerical simulation of welding in shipbuilding. Marine. Technology V, 2003. Pp. 3-20.
24. Feodosiev V.I. Diez conferencias sobre Resistencia de Materiales. Moscú: Editorial MIR, 1993. 179 p.
25. Fogiel M. Problem Solver in Strength of Materials and Mechanics of Solids. New Jersey: Editorial REA, 1988. 1140 p.
26. ASTM A715-98, Standard Specification for Steel Sheet and Strip, High-Strength, Low-Alloy, Hot-Rolled, and Steel Sheet, Cold-Rolled, High-Strength, Low-Alloy, with Improved Formability. www.astm.org.

-
1. Grupo de Investigación en Optimización Energética GIOPEN. Universidad de la Costa, CUC. email hhernand16@cuc.edu.co
 2. Grupo de Investigación GEMAS. Facultad de Ingeniería. Universidad Simón Bolívar, email luis.catellanos@unisimonbolivar.edu.co
 3. Grupo de Investigación en Optimización Energética GIOPEN. Universidad de la Costa, CUC. Email jcabello2@cuc.edu.co
 4. Grupo de Investigación en Optimización Energética GIOPEN. Universidad de la Costa, CUC. email jsilva6@cuc.edu.co
 5. Grupo de Investigación GEMAS. Facultad de Ingeniería. Universidad Simón Bolívar, email c.andres.manga@gmail.com
-

Revista ESPACIOS. ISSN 0798 1015
Vol. 38 (Nº 34) Año 2017

[Índice]

[En caso de encontrar algún error en este website favor enviar email a webmaster]

©2017. revistaESPACIOS.com • Derechos Reservados